

**THIRD ORDER SUSCEPTIBILITY OF SILVER SULFIDE SOL**

**by**


**Dr. Kenneth LaiHing  
Dept. of Chemistry  
Oakwood College  
Huntsville, AL 35896**

**for**

**U.S. Army Missile Command  
Felicia L. Hereford-Kaigler  
Redstone Arsenal  
Huntsville, AL 35898-5254**

**December 28, 1992**

**Contract #DAH01-92-P-R021**

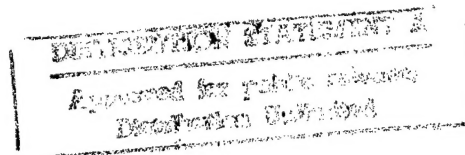

**19970313 087**

**DTIC QUALITY INSPECTED 4**

PLEASE CHECK THE APPROPRIATE BLOCK BELOW:

-AO = U96-04-0343

☐ \_\_\_\_\_ copies are being forwarded. Indicate whether Statement A, B, C, D, E, F, or X applies.

☒ DISTRIBUTION STATEMENT A:  
APPROVED FOR PUBLIC RELEASE: DISTRIBUTION IS UNLIMITED

☐ DISTRIBUTION STATEMENT B:  
DISTRIBUTION AUTHORIZED TO U.S. GOVERNMENT AGENCIES  
ONLY: (Indicate Reason and Date). OTHER REQUESTS FOR THIS  
DOCUMENT SHALL BE REFERRED TO (Indicate Controlling DoD Office).

☐ DISTRIBUTION STATEMENT C:  
DISTRIBUTION AUTHORIZED TO U.S. GOVERNMENT AGENCIES AND  
THEIR CONTRACTORS: (Indicate Reason and Date). OTHER REQUESTS  
FOR THIS DOCUMENT SHALL BE REFERRED TO (Indicate Controlling DoD Office).

☐ DISTRIBUTION STATEMENT D:  
DISTRIBUTION AUTHORIZED TO DoD AND U.S. DoD CONTRACTORS  
ONLY: (Indicate Reason and Date). OTHER REQUESTS SHALL BE REFERRED TO  
(Indicate Controlling DoD Office).

☐ DISTRIBUTION STATEMENT E:  
DISTRIBUTION AUTHORIZED TO DoD COMPONENTS ONLY: (Indicate  
Reason and Date). OTHER REQUESTS SHALL BE REFERRED TO (Indicate Controlling DoD Office).

☐ DISTRIBUTION STATEMENT F:  
FURTHER DISSEMINATION ONLY AS DIRECTED BY (Indicate Controlling DoD Office and Date) or HIGHER  
DoD AUTHORITY.

☐ DISTRIBUTION STATEMENT X:  
DISTRIBUTION AUTHORIZED TO U.S. GOVERNMENT AGENCIES  
AND PRIVATE INDIVIDUALS OR ENTERPRISES ELIGIBLE TO OBTAIN EXPORT-CONTROLLED  
TECHNICAL DATA IN ACCORDANCE WITH DoD DIRECTIVE 5230.25, WITHHOLDING OF  
UNCLASSIFIED TECHNICAL DATA FROM PUBLIC DISCLOSURE, 6 Nov 1984 (Indicate date of determination)  
CONTROLLING DoD OFFICE IS (Indicate Controlling DoD Office).

☐ This document was previously forwarded to DTIC on \_\_\_\_\_ (date) and the  
AD number is \_\_\_\_\_.

☐ In accordance with provisions of DoD instructions, the document requested is not supplied because:

☐ It will be published at a later date. (Enter approximate date, if known).

☐ Other. (Give Reason)

DoD Directive 5230.24, "Distribution Statements on Technical Documents," 18 Mar 87, contains seven distribution statements, as described briefly above. Technical Documents must be assigned distribution statements.

*Per Direction*

*Dr. Laiking / Jim Mayfield*  
Print or Type Name

*ASN 788-8444*  
Telephone Number

*[Signature]*  
Authorized Signature/Date

### Third Order Susceptibility of Silver Sulfide

A silver sulfide sol was prepared by mixing equal concentrations of a silver sol with a sulfur sol. The mixture was stirred for 30 minutes until there was no further change in color.

The sulfur sol was prepared by dissolving solid sulfur in hydrazene followed by addition of distilled water. The mixture was heated at 75 °C for 30 minutes to allow the sol to develop.

The silver sol was prepared by reduction of silver nitrate with a mixture of 10% dextrin and 10% sodium hydroxide. The mixture was stirred for 30 minutes.

The UV-Visible spectrum of the silver sulfide sol is shown in Figure 1. The concentration of this sol was  $1.9 \times 10^{-5}$  M.

The phase conjugate signal intensity was measured using degenerate four-wave mixing (DFWM). The experimental arrangement used for these measurements is shown schematically in Figure 2. Briefly it consisted of a lens A which focuses the beam on the sample. The optical density filter B was used to vary the intensity of all three beams. Beam splitters BS1 (5%T) and BS2 (50%T) were used to generate the probe, front pump and back pumped beams respectively. All beams arrive at the sample simultaneously. The beamsplitter BS3 is used to pick off the conjugate signal which is then focused on a photodiode detector and displayed on a Tektronix 2465 300 MHz oscilloscope. The beam intensity was measured by another detector placed between the sample and the back pumped beam and displayed on another Tektronix oscilloscope.

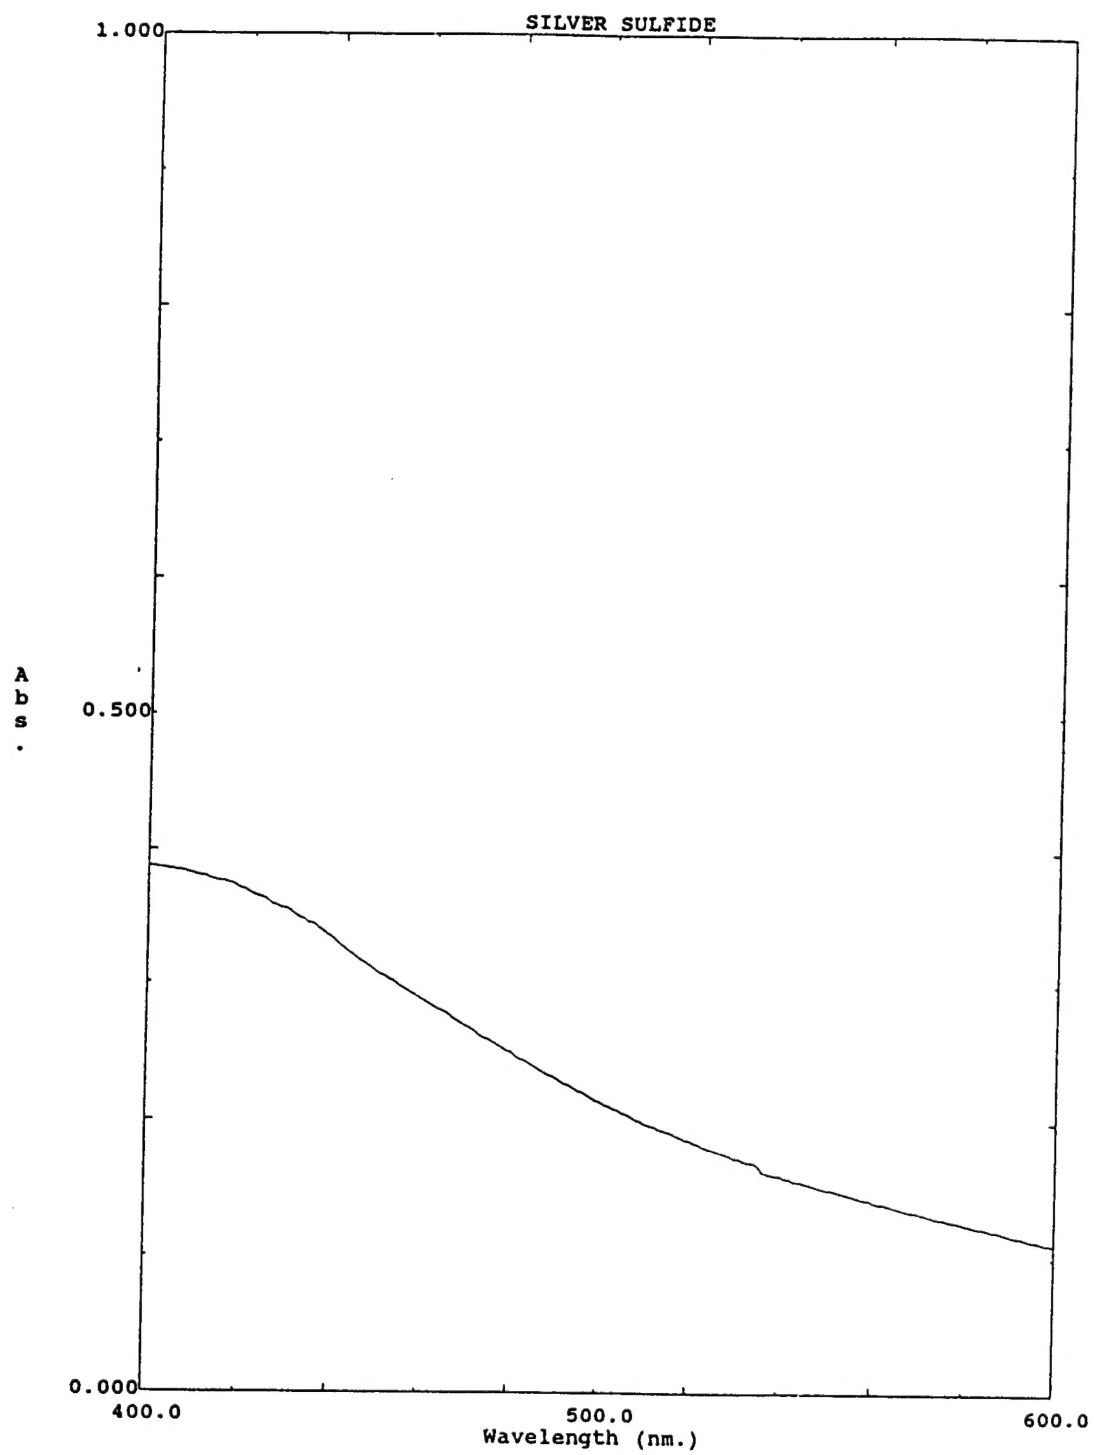


FIGURE 1.

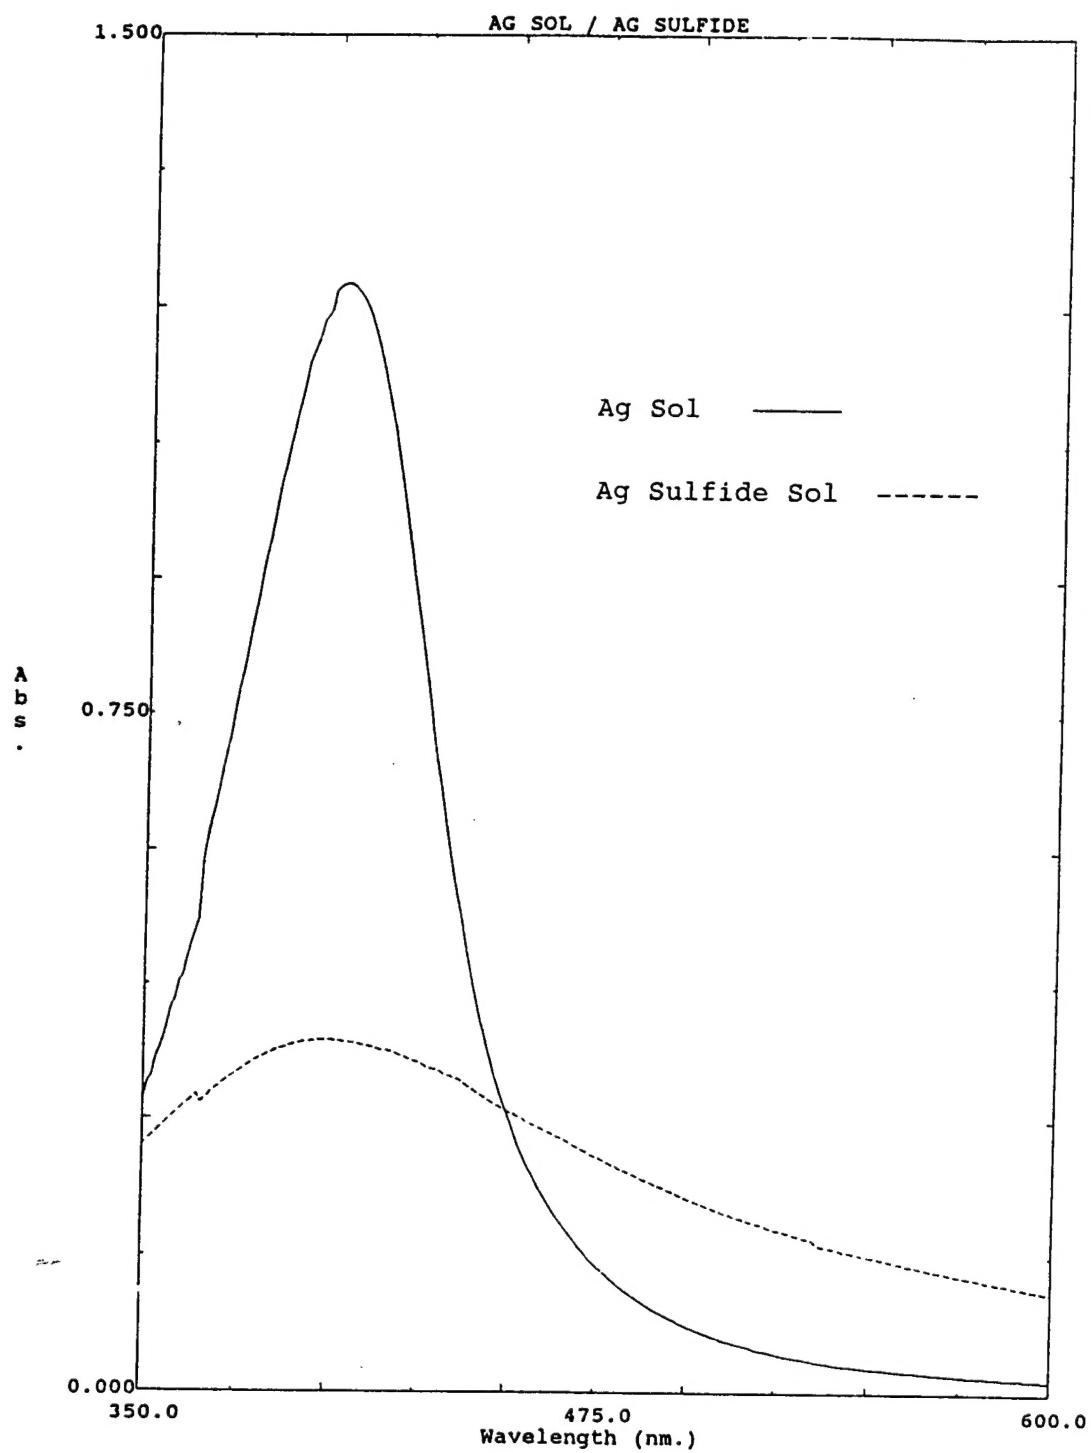


FIGURE 1A.

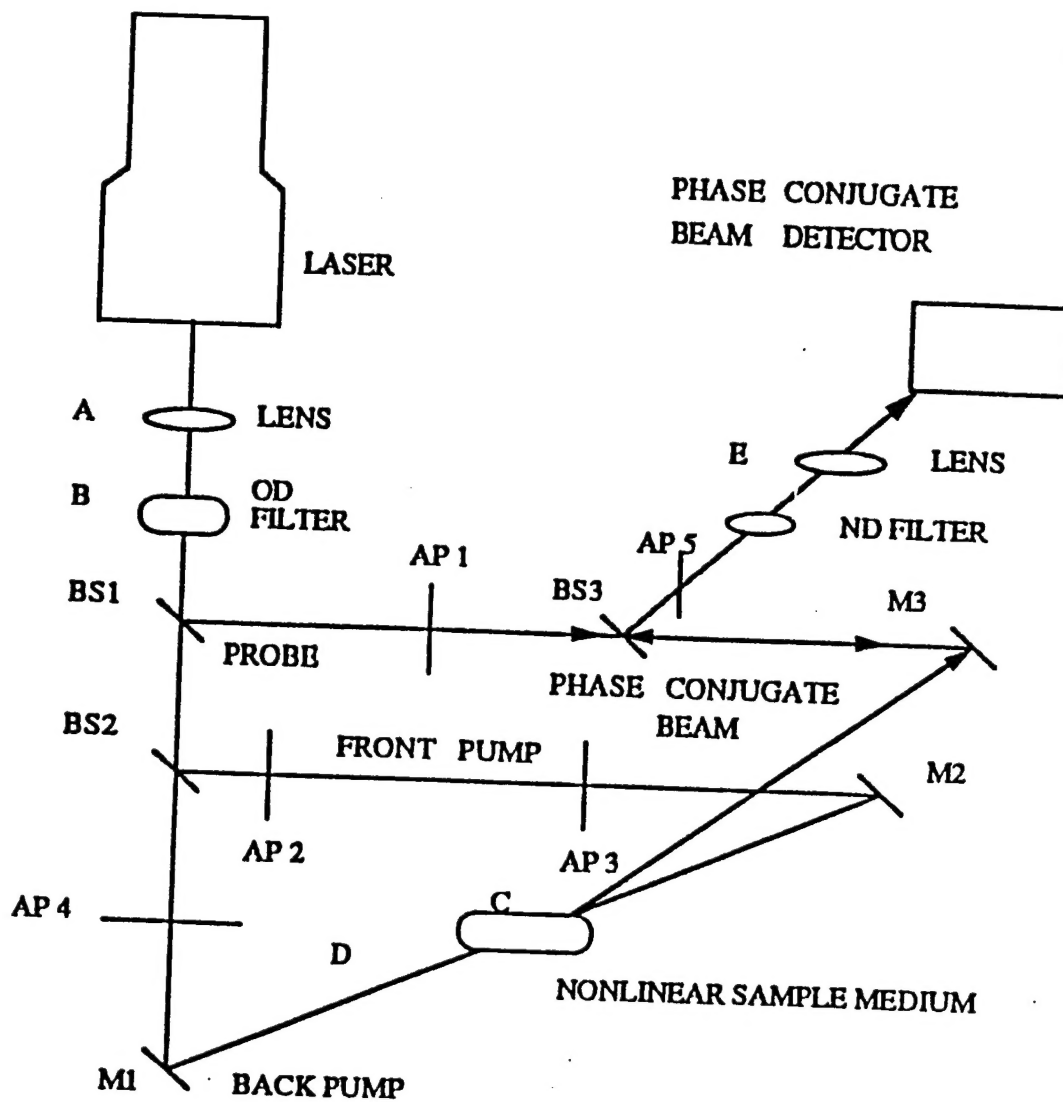


FIGURE 2. Experimental Arrangement for Degenerate Four-Wave Mixing

The value of the phase conjugate signal intensity used in these calculations was obtained from a log-log plot of phase conjugate signal intensity versus laser intensity. A log-log plot of phase conjugate signal intensity versus laser power was also made for carbon disulfide which was used as a reference standard in these experiments.

The value of  $X^3$  for silver sulfide was  $5.4 \times 10^{-12}$  esu.